

No. 1531724.1

(Please quote this number in all correspondence)

CLIENT: Charles Parsons (NZ) Ltd. T/A Line 7 PO Box 38 Auckland 1140	SAMPLE RECEIVED FROM: Charles Parsons (NZ) Ltd.	Date Received: 2.9.24
Attn.: Tina Grant	SAMPLE DESCRIPTION: Lt. brown upholstery fabric – Vintage Nominal Composition – 100% Polyester Nominal Weight – 440gsm	
Client Order No.:	Client Reference:	1 of 3


**AS/NZS 1530.3 – 1999 Methods for Fire Tests on Building Materials, Components and Structures
Part 3: Simultaneous Determination of Ignitability, Flame Propagation,
Heat Release and Smoke Release**

Note: This test was sub-contracted (Test No. 24-003550).
Face Tested: Face

	Standard Error	Mean	
Ignition Time	0.15	9.34 min.	
Flame Propagation Time	Nil	Nil sec.	
Heat Release Integral	3.7	49.1 kJ/m ²	
Smoke Release, log d	0.0210	-0.9145	
Optical Density, d		0.1224 / metre	
Number of Specimens Ignited		6	
Number of Specimens Tested		6	
Regulatory Indices:			
Ignitability Index		11	Range 0-20
Spread of Flame Index		0	Range 0-10
Heat Evolved Index		1	Range 0-10
Smoke Developed Index		4	Range 0-10

"THIS REPORT APPLIES ONLY TO THE SAMPLES TESTED"

Samples and their identifying descriptions have been provided by the client unless otherwise stated. NZWTA Ltd makes no warranty, implied or otherwise as to the source of the tested samples. The above results are designed to provide THE CLIENT WITH GUIDANCE INFORMATION ONLY. This document shall not be reproduced except in full.


C Judan
Key Technical Person

03/10/2024

No. 1531724.1

(Please quote this number in all correspondence)

CLIENT:
Charles Parsons (NZ) Ltd.
T/A Line 7
PO Box 38
Auckland 1140SAMPLE RECEIVED FROM:
Charles Parsons (NZ) Ltd.

Date Received: 2.9.24

Attn.: Tina Grant

SAMPLE DESCRIPTION:
Lt. brown upholstery fabric – Vintage
Nominal Composition – 100% Polyester
Nominal Weight – 440gsm

Client Order No.:

Client Reference:

2 of 3

Each test specimen had an unattached backing of 4.5mm thick fibre reinforced cement board.

Each test specimen was restrained on the exposed face by a layer of galvanised welded square mesh made from wire of nominal diameter 0.8mm and nominal spacing 12mm in both directions and securely fixed to a backing board at four points each 100mm from the centre of the sample and the assembly clamped in four places.

To allow free movement of the sample during testing all corners were folded away from the clamps.

The reaction of thin unsupported flexible materials to flame impingement can be assessed in accordance with AS 1530.2. Where materials of thickness less than 2mm that are sufficiently flexible to be bent by hand around a mandrel of 2mm diameter or less are subjected to the test described herein, they should also be subjected to the test in AS 1530.2.

Specimens tended to flash before ignition. Ignition was based on the occurrence of a single flash of flame which lasted longer than 10 seconds.

The specimens melted and flowed away from the area of maximum heat during the test. Due to this phenomena it should be recognised that this test result may not be a true indication of the product's fire hazard properties.

These results only apply to the specimen mounted, as described in this report. The result of this fire test may be used to directly assess fire hazard, but it should be recognised that a single test method will not provide a full assessment of fire hazard under all fire conditions.

"THIS REPORT APPLIES ONLY TO THE SAMPLES TESTED"

Samples and their identifying descriptions have been provided by the client unless otherwise stated. NZWTA Ltd makes no warranty, implied or otherwise as to the source of the tested samples. The above results are designed to provide THE CLIENT WITH GUIDANCE INFORMATION ONLY. This document shall not be reproduced except in full.


C Judan
Key Technical Person

03/10/2024

No. 1531724.1

(Please quote this number in all correspondence)

CLIENT:
Charles Parsons (NZ) Ltd.
T/A Line 7
PO Box 38
Auckland 1140

SAMPLE RECEIVED FROM:
Charles Parsons (NZ) Ltd.

Date Received: 2.9.24


Attn.: Tina Grant

SAMPLE DESCRIPTION:
Lt. brown upholstery fabric – Vintage
Nominal Composition – 100% Polyester
Nominal Weight – 440gsm

Client Order No.:

Client Reference:

3 of 3

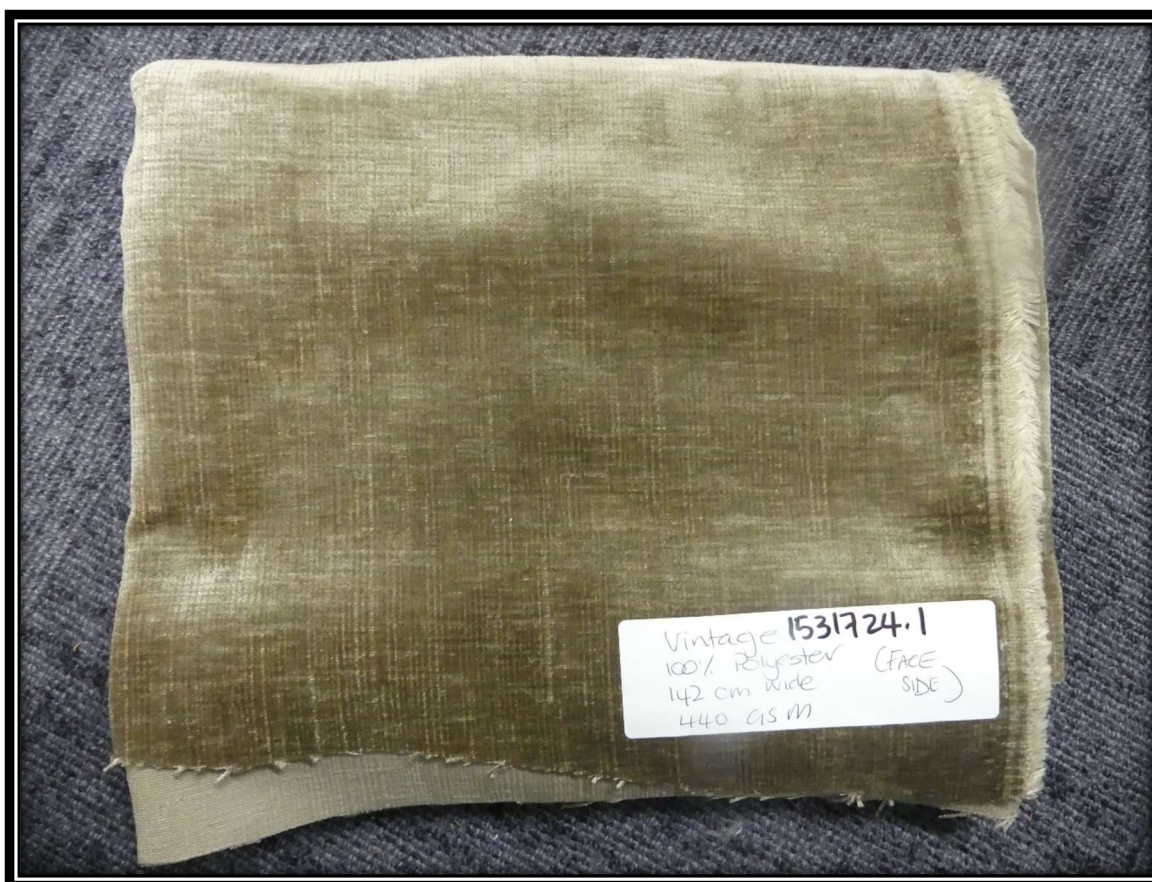

“THIS REPORT APPLIES ONLY TO THE SAMPLES TESTED”

Samples and their identifying descriptions have been provided by the client unless otherwise stated. NZWTA Ltd makes no warranty, implied or otherwise as to the source of the tested samples. The above results are designed to provide THE CLIENT WITH GUIDANCE INFORMATION ONLY. This document shall not be reproduced except in full.


C Judan
Key Technical Person

03/10/2024



This document was created with the Win2PDF "Print to PDF" printer available at

<https://www.win2pdf.com>

This version of Win2PDF 10 is for evaluation and non-commercial use only.

Visit <https://www.win2pdf.com/trial/> for a 30 day trial license.

This page will not be added after purchasing Win2PDF.

<https://www.win2pdf.com/purchase/>